

Bi₂O₃-ZnO-Ta₂O₅ nanopowder synthesized by a soft-chemical route

S. M. Zanetti, M. G. S. Pereira

Laboratório Associado de Sensores e Materiais, Instituto Nacional de Pesquisas Espaciais,
Av. dos Astronautas, 1758 - Jd. da Granja 12227-010, S. J. dos Campos- SP, Brazil
zanetti@las.inpe.br

Keywords: Bi₂O₃-ZnO-Ta₂O₅, cubic bismuth zinc tantalate, pyrochlore, nanopowders, chemical method, Pechini

Abstract: Bismuth zinc tantalate pyrochlore (Bi_{1.5}ZnTa_{1.5}O₇ - α -BZT) belongs to the pyrochlore-based microwave dielectrics, with high ϵ and low dielectric losses. BZT powder was synthesized by a soft-chemical method based on the polymeric precursors. The pyrochlore phase was investigated by X-ray diffraction, ultraviolet-visible and Raman spectroscopy. The study of α -BZT formation reveals that at 600°C a single-phased nanopowder is obtained without any detectable intermediary or secondary phases. The morphology of the powders was examined by scanning electron microscope; the mean size distribution was measured by low angle laser light scattering. Both measurements showed a nanoscaled powder with large agglomerated clusters. The optical gap, obtained from the UV-Vis spectra, ranged from 2.5 to 3.2 eV for the powders treated from 500 to 900°C, respectively.

Introduction

In last years, pyrochlore compounds in the ternary system Bi₂O₃-ZnO-Me₂O₅ (Me= Nb and Ta) have been recognized as potential candidates for capacitor and high-frequency filter applications due to their low-temperature sintering characteristics [1, 2]. With recent developments in microwave devices, the compatibility of sintering ceramic with metal electrodes has been emphasized. One of the main applications of the Bi₂O₃-ZnO-Me₂O₅ (Me= Nb and Ta) ternary system is for manufacturing low-fire high-frequency multilayer capacitors with internal silver electrodes.

The ternary system Bi₂O₃-ZnO-Nb₂O₅ (BZN) has been extensively studied [3-6], however, less attention has been paid to the system Bi₂O₃-ZnO-Ta₂O₅ (BZT). BZT-based dielectrics ceramics have been systematically prepared by the conventional powder processing method and their powders and ceramics studied [7-11]. Youn *et al.*[1] reported the occurrence of recalcitrant secondary phases due to the preferential reaction between Bi₂O₃ and Ta₂O₅ in the conventional processing. It is known that the solid state reaction process can lead to some local chemical heterogeneity and large sized particles, yielding multiphase powders.

Chemical methods have been an alternative for achieving smaller sized particles with chemical homogeneity. It is expected to obtain chemically homogeneous and phase-pure specimens, a narrow size distribution of particles, and low crystallization and sintering

temperatures of the materials when the solution-based chemical methods are employed to prepare nanocrystalline materials

This work aimed principally to achieve chemically homogeneous cubic-BZT nanopowders. For that a soft chemical route was employed via an aqueous polymeric precursor method. The aqueous polymeric precursor is a modified Pechini process [12], and has been successfully used for the synthesis of several complex oxides [13-15].

Experimental

a) Synthesis

The polymeric precursor method consists of chelating metallic cations with citric acid, followed by polymerization through the addition of ethylene glycol. The starting reagents were bismuth oxide, Bi_2O_3 (99.99%, Aldrich), zinc acetate dihydrate, $(\text{CH}_3\text{CO}_2)_2\text{Zn}\cdot 2\text{H}_2\text{O}$ (99.5%, Carlo Erba), and tantalum hydroxide, $\text{Ta}(\text{OH})_5\cdot n\text{H}_2\text{O}$ (99.5%, CIF, S. J. Del Rei-MG, Brazil). The first step involved dissolving tantalum hydroxide in an aqueous solution of oxalic acid (OA), $\text{C}_2\text{H}_2\text{O}_4$ (99%, Fisher), at 80°C . The aqueous suspension of tantalum hydroxide and oxalic acid was heated at boiling until complete dissolution to form tantalum oxalate (molar ratio OA/Ta = 4). The Ta content was gravimetrically determined as Ta_2O_5 . To this solution was added H_2O_2 (30%, Merck) in a molar ratio $\text{H}_2\text{O}_2/\text{metal (Ta+Zn+Bi)} = 4$, and NH_4OH to adjust the pH to 6. After homogenization citric acid (CA), in a molar ratio CA/metal = 3, was added keeping the solution constantly stirred at 60°C . Stoichiometric amounts of zinc acetate dihydrate as salt and Bi_2O_3 , dissolved in an aqueous nitric acid solution (50 v/v %), were added to the solution heated at 60°C to form a (Zn, Nb, Bi) complex precursor. The solution was kept under stirring at 60°C and the pH was adjusted to 6-7 with NH_4OH , resulting in a clear pale yellow solution. Ethylene glycol was added to this solution to promote polymerization of the mixed citrate. In this synthesis, the citric acid/ethylene glycol ratio (CA/EG, mass ratio) was 60/40. Fig. 1 shows the flowchart of the synthesis.

The resin was kept on a hot plate until a viscous gel was obtained, which was then thermally treated at 300°C for 4 h in a furnace. The powder thus obtained was treated at temperatures ranging from 500 to 900°C for 2 h to complete the crystallization process.

a) Characterization

The crystalline phases were determined by X-ray powder diffraction (DRX) using a RIGAKU D/Max 2500 diffractometer, operating with the $\text{CuK}\alpha$ radiation (40kV, 150mA). Raman spectra in the range of 300-1000 nm were obtained with a RENISHAW U-3000 spectrometer furnished with a 632.8 nm He-Ne laser and coupled to an Olympus microscope, and the diffuse reflectance spectra (DRS) were recorded between 300 and 800 nm using a UV-Vis-NIR spectrometer HITACHI, U3501.

The particle size distribution from a sample treated at 700°C for 2 h was determined by lower angle laser light scattering (LALLS) (MASTERSIZER 2000). In addition, a field emission scanning electron microscopy (FE-SEM) (JEOL 6400) was used to examine the morphology of the powders treated at different temperatures.

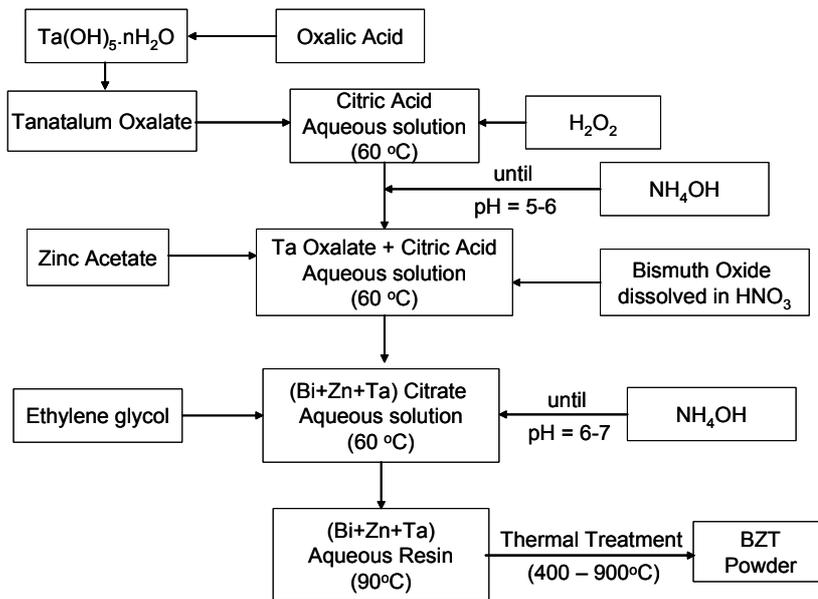


Fig. 1 – Flowchart of BZT synthesis.

RESULTS

The crystalline phase evolution for the α -BZT pyrochlore was followed by XRD, as shown in Fig. 2. At 500°C the powder was amorphous with some evidence of the pyrochlore phase nuclei. At 600°C the pyrochlore phase is already well crystallized although the peaks are some broad indicating small and disordered crystallites. As expected, the increase in the annealing temperature lead to higher crystallinity degree of the samples, as can be observed for powders treated at 700, 800 and 900°C. In this study, no detectable intermediary phases were observed at any time in the cubic-BZT composition, indicating that the chemical synthesis conferred a higher chemical homogeneity and reactivity on the powder. From the broadening of peaks of XRD patterns the crystallite sizes were calculate using the Scherrer equation. Crystallite size presented an exponential growth from 8 to 172 nm at 500 and 900°C, respectively. The results are displayed in Fig. 2b.

Reports in the literature [16] state that the Raman spectrum of cubic BZT pyrochlore shows the followings main bands: 182, 267, 445, 545 and 761 cm^{-1} . Fig. 4 displays the Raman spectra of BZT powders treated at temperatures ranging from 500 – 900°C. The broadness of the features, probably due to the nanometric particles, prevents an accurate estimation of the precise band frequencies. However, the Raman results allow confirming the powder's single-phase nature observed by XRD even when treated at a low temperature (600°C). No extra bands were observed besides the band related to the cubic-BZT phase.

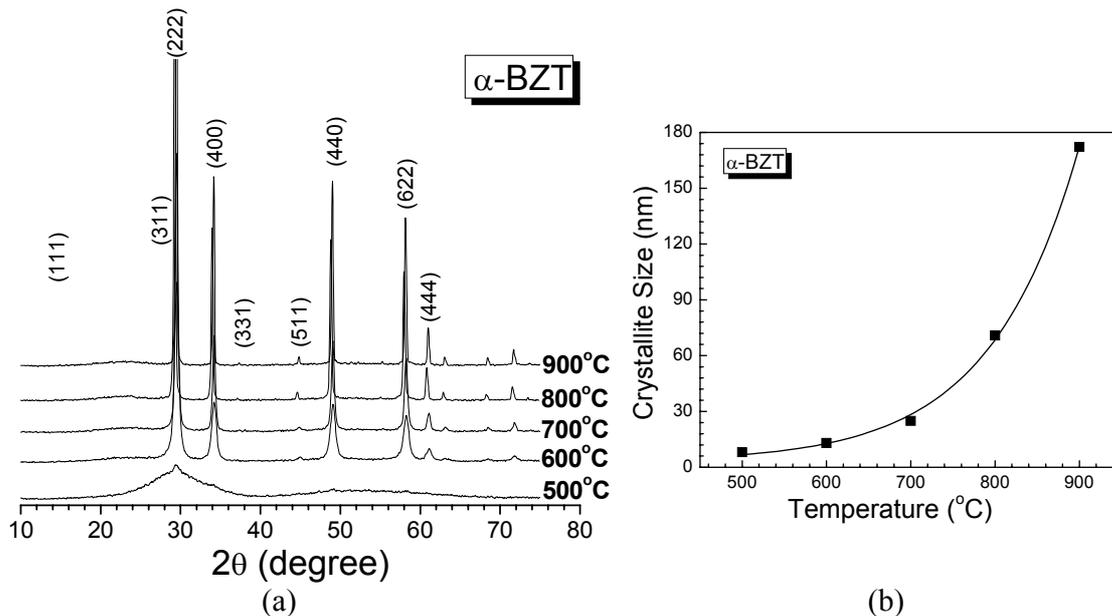


Fig.2 – (a) XRD patterns of BZT powders treated at different temperatures. (b) Crystallite size of BZT powders as a function of the temperature.

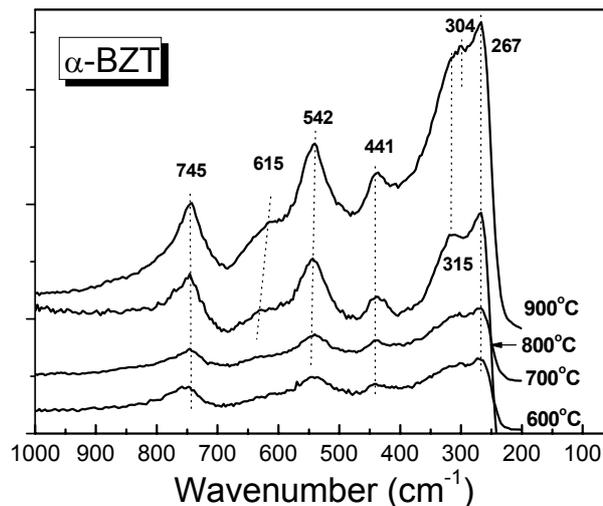


Fig. 3 – Raman spectra of α -BZT powders treated at different temperatures for 2 h.

Fig. 4a shows the evolution of the diffuse reflectance spectra of BZT powders heat-treated at different temperatures. The absorbance values were calculated from the reflectance data, and the inset shows a plot of $(h\nu)^2$ against $h\nu$, from which the direct allowed band gap was estimated [17]. The optical band gaps obtained from these spectra are displayed in Fig. 4b. At 500°C, the band gap was 2.45 eV, indicating highly disordered phase, in accordance with the XRD data. At 600°C, the band gap increased to 3.38 eV. As the temperature increased, the band gap decreased to approximately 3.2 eV in the powders treated from 700 to 900°C, which is in agreement with the reported value (3.1 eV). The

higher band gap value observed in the powder treated at 600°C may be attributed to the crystallite size (15 nm).

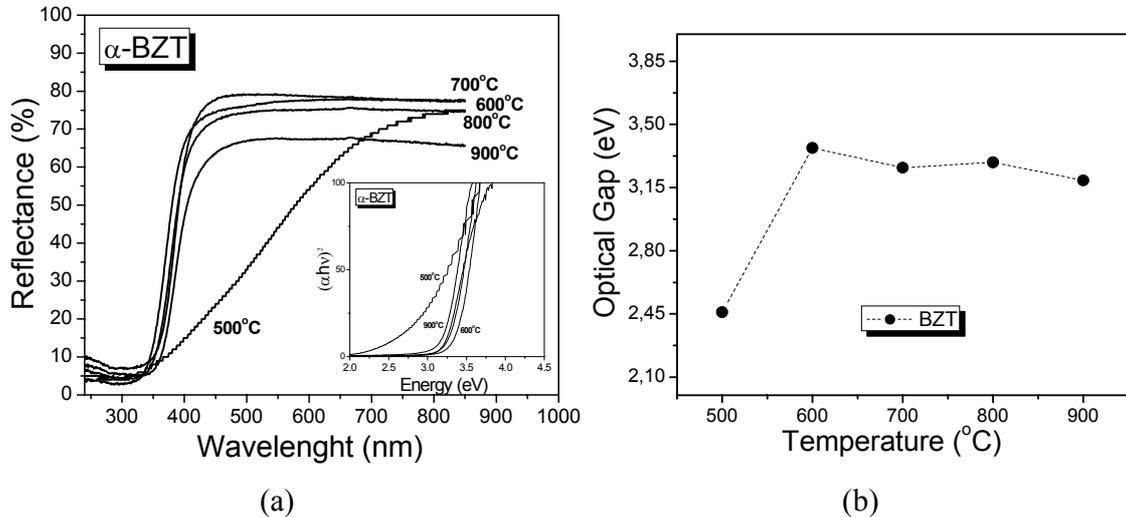


Fig. 4: (a) Diffuse reflectance of the BZT powders treated at temperatures from 500 to 900°C; (b) Optical gap as a function of the temperature.

The evolution of particle growth in the powders treated at different temperatures, was observed by SEM, the images clearly reveal the variation of the particle growth with thermal treatment (not shown). The powders treated from 500 to 700°C are composed of large agglomerated clusters with dimensions of hundreds of nanometers, while annealing at 800°C led to the formation of larger particles, while the thermal treatment at 900°C gave rise to homogeneous sintered clusters with grain sizes exceeding 1 μm . The powder treated at 700°C was ball milled in isopropyl alcohol for 6 h in order to break big aggregates (Fig. 5a). The particle size distribution was measured by low angle laser light scattering in aqueous solution and the powder showed particles around 156 nm in diameter coexisting with reminiscent aggregates, as can be observed in Fig. 5b.

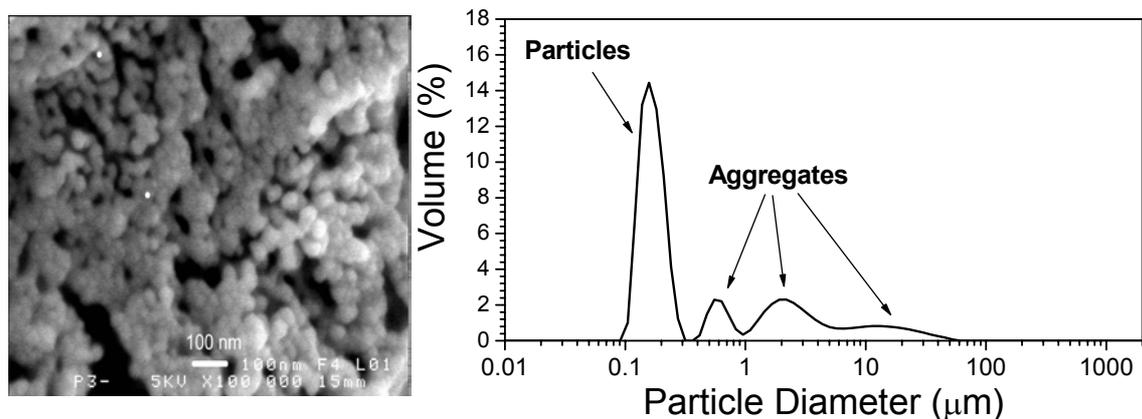


Fig. 5 - BZT powder treated at 700°C: (a) SEM image; (b) Particle size distribution measured by low angle laser light scattering.

Conclusion

$\text{Bi}_2\text{O}_3\text{-ZnO-Ta}_2\text{O}_5$ nanopowder was successfully synthesized by a soft-chemical route based on the polymeric precursor method. The study of phase formation revealed that a well crystallized single-phased nanopowder was obtained after calcination at 600°C . The single-phase nature of the powder was confirmed by Raman spectra. The optical band gap for the powders treated between 600 and 900°C , calculated from diffuse reflectance spectra, was $3.4 - 3.2$ eV, indicating the low temperature crystallization of the pyrochlore phase. The low crystallization temperature and the phase purity of the nanopowder were attributed to the material's high chemical homogeneity and reactivity achieved by the chemical route.

Acknowledgement

The work was supported by the Brazilian financing agency FAPESP. The authors would like to thank LCSIM – Université de Rennes I - France, for the FE-SEM facilities, and LIEC – UFSCar – Brazil, for the XRD measurements.

References

- [1] H-J Youn, T. Sogabe, C. A. Randall, T. R. Shrout, M. T. Lanagan, *J. Am. Ceram. Soc.* 84 (2001), p.2557
- [2] A. Chen, Y. Zhi, H-J Youn, C. A. Randall, A. S. Bhalla, E. L. Cross, M. T. Lanagan, *Appl. Phys. Lett.* 82 (2003), p.3734.
- [3] J.C. Nino, M.T. Lanagan, C.A. Randall, *J. Mat. Res.* 16 (2001), p.1460.
- [4] S.Y. Chen, S.Y. Lee, Y.J. Lin, *J. Eur. Cer. Soc.* 23 (2003), p.873.
- [5] X.L. Wang, H. Wang, X. Yao, *J. Am. Cer. Soc.* 80 (1997), p.2745.
- [6] H. Wang, H. Du, X. Yao, *Mat. Sci. Eng. B* 99 (2003), p.20.
- [7] H-J Youn, C. A. Randall, A. Chen, T. R. Shrout, M. T. Lanagan, *J. Mater. Res.* 17 (2002), p.1502.
- [8] D. Peng, B. Shen, L. Zhang, X. Yao, *Ceram. Int.* 30 (2004), p.1199.
- [9] B. Shen, J. Zhai, X. Yao, *Appl. Phys. Lett.* 86 (2005), p.072902.
- [10] B. Shen, X. Yao, D. Peng, L. Kang, *Ceram. Int.* 30 (2004), p.1207.
- [11] B. Shen, X. Yao, L. Kang, D. Peng, *Ceram. Int.* 30 (2004), p.1203.
- [12] M. Pechini, US Patent No. 3.330.697, 1967.
- [13] S. M. Zanetti, E. R. Leite, E. Longo, J. A. Varela, *J. Eur. Cer. Soc.* 19 (1999), p.1409.
- [14] S. M. Zanetti, E. R. Leite, E. Longo, *et al.*, *J. Mater. Res.* 15 (2000), p.2091.
- [16] E.C. Paris, E.R. Leite, E. Longo, J.A. Varela, *Mater. Lett.* 37 (1998), p.1.
- [16]. H. Du, X. Yao, *J. Mater. Sci: Mater. Electron.* 15 (2004), p.613.
- [17] B. M. Weckhuysen, R. A. Schoonheydt, *Catal. Today* 49 (1999), p.441.